


This MotoCAP safety rating applies to:

Brand: DriRider
Model: Nordic 2
Type: Pants - Textile
Date purchased: 23 October 2018
Sizes tested: XL
Gender: M
Style: Tourer
Test code: P18T03

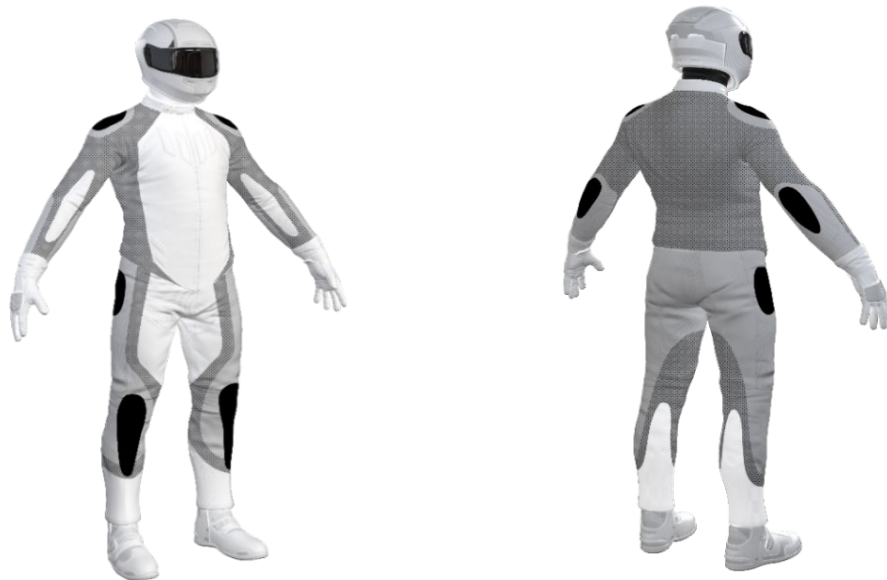
Test Results Summary:

	Rating	Score
MotoCAP Protection Rating	↘	-10.1
Abrasion	1/10	-4.28
Burst	10/10	1129
Impact	1/10	0.0
MotoCAP Comfort Rating	↘	0.085
Moisture Vapour Resistance		175.0
Thermal Resistance		0.249
Water resistance	3/10	18.6

This garment is fitted with impact protectors for the knees and with pockets for aftermarket impact protectors for the hips. This garment does not provide vents to aid cooling in hot weather.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.


Zone 1


High risk of abrasion
High risk of impact

Abrasion Resistance
Zone 2


High risk of abrasion

Zone 3


Medium risk of abrasion

Zone 4


Low risk of abrasion

The garment was tested for abrasion resistance in accordance with MotoCAP test protocols. The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone.

Details of materials used in garment:

Material A:	Single layer of leather shell, foam liner, water resistant liner, mesh inner liner
Material B:	Polyester woven fabric shell, water resistant liner and mesh inner liner
Material C:	Woven elastic fabric, water resistant liner and mesh inner liner

Zone	Coverage (%)	Abrasion time for each test (seconds)						Average (seconds)	
		1	2	3	4	5	6		
Zone 1 and 2 areas (High abrasion risk)									
Material A	30%	10.00	10.00	6.95	6.78	10.00		8.75	G
Material B	70%	0.48	0.38	0.43	0.50	0.40	0.47	0.44	P
Zone 3 area (Medium abrasion risk)									
Material B	70%	0.48	0.38	0.43	0.50	0.40	0.47	0.44	P
Material C	30%	0.17	0.15	0.18	0.25			0.19	P
Zone 4 area (Low abrasion risk)									
Material B	100%	0.48	0.38	0.43	0.50	0.40	0.47	0.44	M

The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table above. The colour coding is based on the worst performing material in each zone.



Determining Criteria		Good	Acceptable	Marginal	Poor
High abrasion risk	Zone 1/2:	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3:	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4:	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Burst Strength

The garment’s burst strength was tested in accordance with MotoCAP test protocols. The table below shows

the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

Burst pressure (kPA)

Area	1	2	3	4	5	Average	
Zones 1 & 2	1091	1030	1494	484	1341	1088	G
Zone EZ	607	997	1508	666	1470	1050	G
Zones 3 & 4	1029	1699	1322	1566	1232	1369	G

The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table above.



Impact Protection

The garment was tested for impact protection and coverage in accordance with MotoCAP test protocols.

The table below shows the test results for each strike on each impact protector in kilonewton (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee			Hip		
Average force (kN)	29.9	M		P		
Maximum force (kN)	33.7	P		P		
Coverage of zone 1 area	140%			0%		
Coverage of zone after displacement	90%			0%		
Individual test results						
Impact force (kN)	Knee			Hip		
Strike location	A	B	C	No impact protector present		
	A	B	C	A	B	C
Impact Protector 1	29.4	27.0	26.8			
Impact Protector 2	29.5	27.3	31.7			
Impact Protector 3	31.5	31.8	33.7			

The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table above. The colour coding is based on the worst performing score for average or maximum force for each impact zone.



Determining Criteria	Good	Acceptable	Marginal	Poor*
Impact force (kN)	 < 15	 15 - 24	 25 - 30	 > 30

* Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Thermal comfort

The garment was tested for thermal comfort following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

	1	2	Average
Moisture Vapour Resistance - R_{et} (kPam ² /W)	162.2	187.8	175.0

	1	2	Average
Thermal Resistance - R_{ct} (Km ² /W)	0.236	0.262	0.249

Water spray and rain resistance

This garment is advertised as water-resistant, and so has been tested for water spray and rain resistance according to the MotoCAP test protocols. The table below shows the increased weight (g) and proportion (%) of the garment and undergarments due to water absorption.

	Water absorbed by garment		Water absorbed by underwear	
	Mass (g)	Percentage (%)	Mass (g)	Percentage (%)
Pants 1	218.7	16%	308.4	22%
Pants 2	173.4	12%	211.6	15%
Average	196.0	14%	260.0	19%

Location of wetting:

Visible wetting to the cotton undergarment worn under the motorcycle water resistant pants was present at the waistband, the crotch, the upper legs and lower legs