



# This MotoCAP safety rating applies to:

Brand Ixon Model Raptor

Type Jacket - Textile
Date purchased 12 September 2022

Sizes tested XL and 2XL Test garment gender Male


Style All Purpose RRP \$339.95

<b>Test Results Summary</b>	Rating	Score
MotoCAP Protection Rating	**	30.8
Abrasion	1/10	0.50
Burst	10/10	1584
Impact	6/10	41.5
MotoCAP Breathability Rating	**	0.303
Moisture Vapour Resistance	-	57.2
Thermal Resistance	-	0.289
Water resistance	8/10	2.7

This garment is fitted with impact protectors for the elbows and shoulders. A pocket is provided for an aftermarket back protector. Mesh panels are located in the arms, chest and back to allow airflow movement through the garment. This garment has a removable water-resistant liner. The breathability rating above was achieved with the thermal and water-resistant liners removed. When tested with the water-resistant liner installed, the breathability rating reduced to 1 star.

### **Jacket and Pants - Crash Impact Risk Zones**

This diagram is a pictorial representation of the crash impact risk Zones.

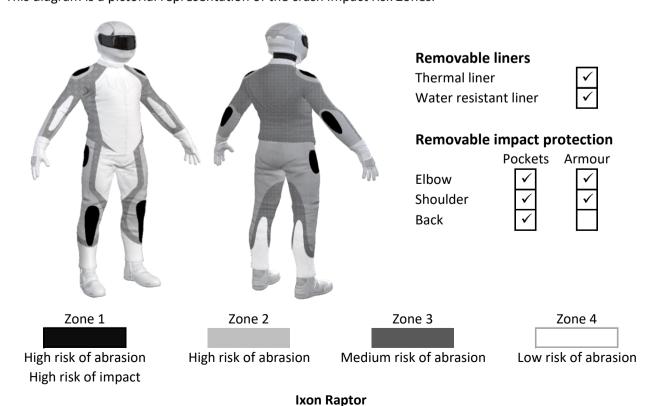



#### **Abrasion Resistance**

The jacket was tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



#### **Abrasion Resistance Performance**

Abrasion rating	1/10
Abrasion score	0.50

<b>Determining Criteria</b>	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zone 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

**Individual Abrasion Resistance Results:** - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

#### Abrasion time for each test (seconds)

Zone 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	40%	1.15	1.09	1.18	0.93			1.09	Р
Material B	60%	0.69	0.63	0.61	0.77	0.66	0.64	0.67	Р
Zone 3	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material B	60%	0.69	0.63	0.61	0.77	0.66	0.64	0.67	Р
Material C	40%	0.74	0.54	0.49	0.52	0.54	0.55	0.57	Р
Zone 4	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	_
Material B	60%	0.69	0.63	0.61	0.77	0.66	0.64	0.67	М
Material C	40%	0.74	0.54	0.49	0.52	0.54	0.55	0.57	М

#### Details of materials used in jacket

Material A	Woven fabric shell, foam layer and mesh inner liner
Material B	Woven fabric shell and mesh inner liner

Material C Double mesh fabric shell with mesh inner liner



# **Burst Strength**

The jacket was tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



## **Burst Strength Performance**

Burst rating	10/10
Burst score	1584

<b>Determining Criteria</b>	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

**Individual Burst Strength Results:** - The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

# Burst pressure for each seam (kPA)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	1809	1839	1512	1737	1584	1659	1690	G
Zones 3 & 4	1236	1168	1210	1082	1202	1052	1158	G



#### **Impact Protection**

The jacket was tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance
Impact rating 6/10
Impact score 41.5

<b>Determining Criteria</b>	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

<sup>\*</sup> Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

**Individual Impact Protector Results:** - The table below shows the test results for each strike on each impact protector in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone. Individual strike results are capped at a maximum of 50kN.

Impact protector type	Elbow		Shoulder
Average force (kN)	11.7	G	11.7 <b>G</b>
Maximum force (kN)	15.9	A	15.9 A
Coverage of Zone 1 area	70%	<del></del>	100%
Coverage of Zone after displacement	50%		90%

**Individual Impact Protector Results:** - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

### Force transfer for each impact strike (kN)

Impact protector type	Elbow			Shoulder		
Strike location	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	8.9	13.1	12.0	8.9	13.1	12.0
Impact Protector 2	9.9	10.7	15.9	9.9	10.7	15.9
Impact Protector 3	10.5	9.3	14.7	10.5	9.3	14.7



# Breathability

The jacket was tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable li	With	water-resista	int liner		
Breathability rating	Breat	hability rating	*		
Breathability score	0.303	Breathability score		0.286	
Moisture Vapour Resis	tance - R <sub>et</sub> (kPa.m²/W)	1	2	Average	
Without removable liners	}	62.4	52.0	57.2	
With water-resistant liner		82.7	92.8	87.8	
Thermal Resistance - R	R <sub>ct</sub> (K.m²/W)	1	2	Average	
Without removable liners	1	0.287	0.292	0.289	
With water-resistant liner		0.417	0.418	0.418	

# Water spray and rain resistance

This jacket is advertised as water-resistant, and so has been tested for water spray and rain resistance according to the MotoCAP test protocols. The table below shows the water absorbed (ml) and the wetting proportion (%) of the garment and undergarments due to water absorption.

	Water absorbed by garment		Water absorbed by underwear	
	Volume (ml)	Percentage (%)	Volume (ml)	Percentage (%)
Jacket 1	523	38%	7	2.3%
Jacket 2	569	42%	9	3.0%
Average	546	40%	8	2.7%

### **Location of wetting**

There was no visible wetting to the cotton underwear for either jackets tested.

Jacket - Textile	
mber 2022	
Deakin University	
MotoCAP Chief Scientist	
J21T14	
January 2023	
y 2023	
)	y 2023