



This MotoCAP safety rating applies to:

Brand 1Tonne

Model Fury Blue Armoured
Type Pants - Denim
Date purchased 22 May 2023
Sizes tested 36 and 38
Test garment gender Male
Style All Purpose


RRP \$189.00

Test Results Summary	Rating	Score
MotoCAP Protection Rating	***	41.6
Abrasion	3/10	2.74
Burst	10/10	1284
Impact	7/10	50.1
MotoCAP Breathability Rating	***	0.449
Moisture Vapour Resistance	-	34.4
Thermal Resistance	-	0.258
Water resistance	N/A	N/A

This garment is fitted with impact protectors for the knees and hips. There are no vents to allow airflow movement through the garment.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.

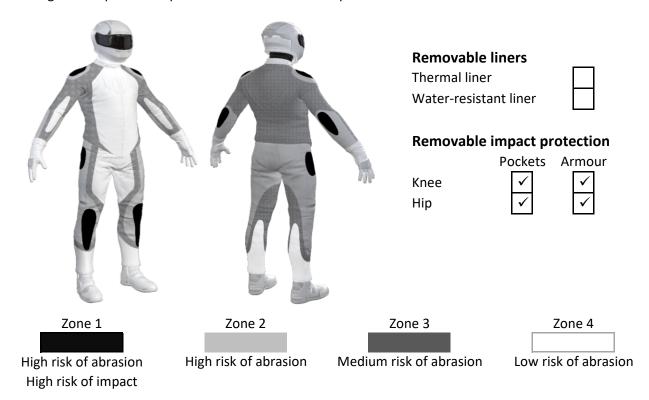



Abrasion Resistance

These pants were tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



Abrasion Resistance Performance

Abrasion rating 3/10 Abrasion score 2.74

Determining Criteria	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Individual Abrasion Resistance Results: - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

Abrasion time for each test (seconds)

for each test (sec	conds)						
Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
100%	3.08	2.26	3.40	4.17	1.74	2.82	2.91 M
Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
100%	3.08	2.26	3.40	4.17	1.74	2.82	2.91 G
Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
50%	3.08	2.26	3.40	4.17	1.74	2.82	2.91 G
50%	0.54	0.71	0.73	0.49	0.67	0.39	0.59 M
	Coverage (%) 100% Coverage (%) 100% Coverage (%) 50%	100% 3.08 Coverage (%) Sample 1 100% 3.08 Coverage (%) Sample 1 50% 3.08	Coverage (%) Sample 1 Sample 2 100% 3.08 2.26 Coverage (%) Sample 1 Sample 2 100% 3.08 2.26 Coverage (%) Sample 1 Sample 2 50% 3.08 2.26	Coverage (%) Sample 1 Sample 2 Sample 3 100% 3.08 2.26 3.40 Coverage (%) Sample 1 Sample 2 Sample 3 100% 3.08 2.26 3.40 Coverage (%) Sample 1 Sample 2 Sample 3 50% 3.08 2.26 3.40	Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 100% 3.08 2.26 3.40 4.17 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 100% 3.08 2.26 3.40 4.17 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 50% 3.08 2.26 3.40 4.17	Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 100% 3.08 2.26 3.40 4.17 1.74 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 100% 3.08 2.26 3.40 4.17 1.74 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 50% 3.08 2.26 3.40 4.17 1.74	Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 Sample 6 100% 3.08 2.26 3.40 4.17 1.74 2.82 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 Sample 6 100% 3.08 2.26 3.40 4.17 1.74 2.82 Coverage (%) Sample 1 Sample 2 Sample 3 Sample 4 Sample 5 Sample 6 50% 3.08 2.26 3.40 4.17 1.74 2.82

Details of materials used in pant

Material A Denim fabric shell, para-aramid fabric layer and mesh inner liner Material B Denim fabric shell



Burst Strength

These pants were tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



Burst Strength Performance				
Burst rating	10/10			
Burst score	1284			

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

Individual Burst Strength Results: - The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

Burst pressure for each seam (kPA)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Zones 1 & 2	1151	1413	1599	1749	1628	1188	1455 G
Zones 3 & 4	671	616	773	530	435	587	602 M



Impact Protection

These pants were tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance Impact rating 7/10

Impact score

50.1

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

^{*} Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Impact Protector Results: - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee		Hip
Average force (kN)	16.7	A	14.4 G
Maximum force (kN)	23.5	A	16.7 A
Coverage of Zone 1 area	95%		135%
Coverage of Zone after displacement	80%		100%

Individual Impact Protector Results: - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

Force transfer for each impact strike (kN)

Impact protector type	Knee			Hip		
Strike location	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	15.1	15.5	16.8	13.5	13.8	16.7
Impact Protector 2	15.2	16.8	16.1	13.8	13.6	14.8
Impact Protector 3	15.5	15.7	23.5	14.4	15.2	14.2



Breathability

These pants were tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable I	With water-resistant liner					
Breathability rating	***	Brea	Breathability rating			
Breathability score 0.449		Brea	N/A			
Moisture Vapour Resis	stance - R _{et} (kPa.m²/W)	1	2	Average		
Without removable liner	S	35.1	33.8	34.4		
With water-resistant line	er	N/A	N/A	N/A		
Thermal Resistance -	R _{ct} (K.m²/W)	1	2	Average		
Without removable liner	S	0.252	0.263	0.258		
With water-resistant line	er	N/A	N/A	N/A		

Water spray and rain resistance

This pants have not been advertised as water-resistant so has not been tested for water spray and rain resistance.

Assessment Details.

Brand 1Tonne

Model Fury Blue Armoured
Type Pants - Denim
Date purchased 22 May 2023

Tested by AMCAF, Deakin University Report approved by MotoCAP Chief Scientist

Garment test reference P23D06
Rating first published August 2023
Rating updated 9 August 2023