





### This MotoCAP safety rating applies to:

**Brand** Rev'It Model Dean SF Type Pants - Textile Date purchased 14 February 2024 Sizes tested 34 and 36

Male Test garment gender Style All Purpose


RRP \$338.95

Test Results Summary	Rating	Score
MotoCAP Protection Rating	**	29.9
Abrasion	1/10	1.07
Burst	10/10	1073
Impact	6/10	46.0
MotoCAP Breathability Rating	***	0.484
Moisture Vapour Resistance	-	21.8
Thermal Resistance	-	0.176
Water resistance	N/A	N/A

This garment is fitted with impact protectors for the knees and hips. There are no vents to allow airflow movement through the garment.

# **Jacket and Pants - Crash Impact Risk Zones**

This diagram is a pictorial representation of the crash impact risk Zones.

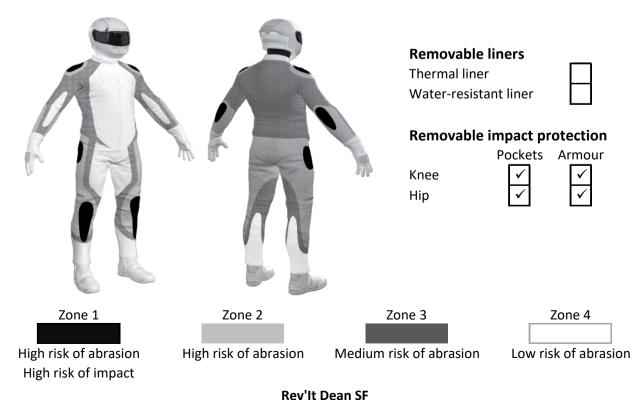



### **Abrasion Resistance**

These pants were tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



#### **Abrasion Resistance Performance**

Abrasion rating	1/10
Abrasion score	1.07

<b>Determining Criteria</b>	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

**Individual Abrasion Resistance Results:** - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

# Abrasion time for each test (seconds)

Zones 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Material A	100%	1.35	0.88	0.89	1.48	0.91	0.90	1.07 <b>F</b>
Zone 3	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Material A	100%	1.35	0.88	0.89	1.48	0.91	0.90	1.07
Zone 4	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Material A	100%	1.35	0.88	0.89	1.48	0.91	0.90	1.07

### Details of materials used in pant

Material A Woven fabric shell



### **Burst Strength**

These pants were tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



Burst Strength Performance				
Burst rating	10/10			
Burst score	1073			

<b>Determining Criteria</b>	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

**Individual Burst Strength Results:** - The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

### Burst pressure for each seam (kPA)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	820	1100	1325	1447	782	989	1077	G
Zones 3 & 4	998	1026	831	1164	1248	1068	1056	G



#### **Impact Protection**

These pants were tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance
Impact rating 6/10
Impact score 46.0

<b>Determining Criteria</b>	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

<sup>\*</sup> Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

**Impact Protector Results:** - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee		Hip	
Average force (kN)	16.7	A	22.8	Α
Maximum force (kN)	17.5	Α	25.1	M
Coverage of Zone 1 area	120%		115%	
Coverage of Zone after displacement	90%		100%	

**Individual Impact Protector Results:** - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

## Force transfer for each impact strike (kN)

Impact protector type	Knee			Hip		
Strike location	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	15.6	15.9	16.9	21.9	23.4	25.1
Impact Protector 2	17.5	17.1	17.2	22.7	22.9	22.5
Impact Protector 3	16.3	16.8	16.8	22.7	23.7	20.5



### Breathability

These pants were tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable I	With	ant liner		
Breathability rating  Breathability score  ∴ ★★  0.484		Brea	thability rating	N/A
		Brea	N/A	
Moisture Vapour Resis	stance - R <sub>et</sub> (kPa.m²/W)	1	2	Average
Without removable liner	S	22.3	21.3	21.8
With water-resistant line	er	N/A	N/A	N/A
Thermal Resistance - I	R <sub>ct</sub> (K.m²/W)	1	2	Average
Without removable liner	S	0.187	0.165	0.176
With water-resistant line	er	N/A	N/A	N/A

### Water spray and rain resistance

This pants have not been advertised as water-resistant so has not been tested for water spray and rain resistance.

Assessment	Detai	ls.
------------	-------	-----

Brand Rev'lt

Model Dean SF

Type Pants - Textile

Date purchased 14 February 2024

Tested by AMCAF, Deakin University
Report approved by MotoCAP Chief Scientist

Garment test reference P24T05
Rating first published April 2024
Rating updated 8 April 2024