



This MotoCAP safety rating applies to:


Brand	Alpinestars
Model	Bogota Pro Drystar
Type	Pants - Textile
Date purchased	20 January 2024
Sizes tested	L and XL
Test garment gender	Male
Style	All Purpose
RRP	\$499.00

Test Results Summary	Rating	Score
MotoCAP Protection Rating	★★	34.1
Abrasion	2/10	1.42
Burst	10/10	1384
Impact	6/10	43.9
MotoCAP Breathability Rating	★★	0.326
Moisture Vapour Resistance	-	49.3
Thermal Resistance	-	0.268
Water resistance	9/10	2.4

This garment is fitted with impact protectors for the knees and hips. Replacing the hip armour with higher performing impact protectors would improve the protection levels of this garment. There are zipped vents in the front of legs to allow controlled airflow movement through the garment. The breathability rating is based on tests of the garment's materials when all vents are closed. The breathability of this product may be better when the vents are open. This garment has a removable water-resistant liner. The breathability rating above was achieved with the water-resistant liner removed. When tested with the water-resistant liner installed, the breathability rating reduced but remained within the 2 star range.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.

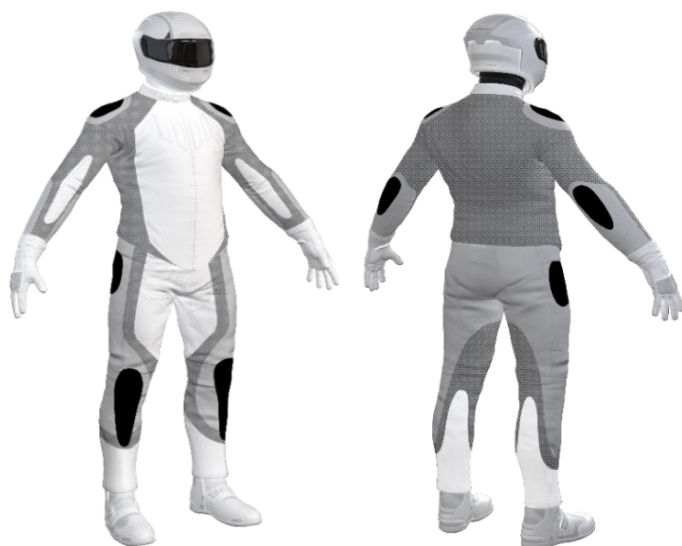

Zone 1

High risk of abrasion
High risk of impact

Zone 2

High risk of abrasion

Zone 3

Medium risk of abrasion

Zone 4

Low risk of abrasion

Removable liners

Thermal liner	<input type="checkbox"/>
Water-resistant liner	<input checked="" type="checkbox"/>

Removable impact protection

	Pockets	Armour
Knee	<input checked="" type="checkbox"/>	<input checked="" type="checkbox"/>
Hip	<input checked="" type="checkbox"/>	<input checked="" type="checkbox"/>

Abrasion Resistance

These pants were tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



Abrasion Resistance Performance

Abrasion rating	2/10
Abrasion score	1.42

Determining Criteria	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Individual Abrasion Resistance Results: - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

Abrasion time for each test (seconds)

Zones 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	65%	3.56	3.50	6.42	3.20	7.20	10.00	5.65	G
Material B	35%	0.71	0.71	0.82	0.49	0.49	0.48	0.62	P
Zone 3	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material A	50%	3.56	3.50	6.42	3.20	7.20	10.00	5.65	G
Material B	50%	0.71	0.71	0.82	0.49	0.49	0.48	0.62	P
Zone 4	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Material B	100%	0.71	0.71	0.82	0.49	0.49	0.48	0.62	M

Details of materials used in pant

Material A	Woven fabric shell over woven fabric layer with mesh inner liner
Material B	Woven fabric shell with mesh inner liner

Burst Strength

These pants were tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



Burst Strength Performance

Burst rating	10/10
Burst score	1384

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

Individual Burst Strength Results: - The table below shows the burst pressure in kilopascals (kPa) for each sample tested by Zone and the average result for each zone.

Burst pressure for each seam (kPa)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	1225	2007	1570	1094	1217	1786	1483	G
Zones 3 & 4	1328	974	1204	837	851	734	988	A

Impact Protection

These pants were tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance

Impact rating 6/10
Impact score 43.9

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

* Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Impact Protector Results: - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee		Hip	
Average force (kN)	14.2	G	24.5	A
Maximum force (kN)	18.0	A	25.4	M
Coverage of Zone 1 area	100%		150%	
Coverage of Zone after displacement	50%		100%	

Individual Impact Protector Results: - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

Force transfer for each impact strike (kN)

Impact protector type	Knee			Hip		
	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	12.9	13.3	12.9	25.4	24.9	23.8
Impact Protector 2	14.1	13.9	14.6	24.5	23.5	25.0
Impact Protector 3	14.0	14.6	18.0	24.0	24.7	25.1

Breathability

These pants were tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable liners

Breathability rating	★★
Breathability score	0.326

With water-resistant liner

Breathability rating	★★
Breathability score	0.309

Moisture Vapour Resistance - R_{et} (kPa.m ² /W)	1	2	Average
Without removable liners	51.9	46.7	49.3
With water-resistant liner	62.3	69.0	65.6
Thermal Resistance - R_{ct} (K.m ² /W)	1	2	Average
Without removable liners	0.270	0.265	0.268
With water-resistant liner	0.335	0.341	0.338

Water spray and rain resistance

This pants are advertised as water-resistant, and so has been tested for water spray and rain resistance according to the MotoCAP test protocols. The table below shows the water absorbed (ml) and the wetting proportion (%) of the garment and undergarments due to water absorption.

	Water absorbed by garment		Water absorbed by underwear	
	Volume (ml)	Percentage (%)	Volume (ml)	Percentage (%)
Pants 1	347	23%	9	4%
Pants 2	316	21%	3	1%
Average	332	22%	6	2%

Location of wetting

Minor wetting to the cotton underwear was present at the waistband and lower legs for one of the pants tested, there was no visible wetting to the other pair of pants tested.

Assessment Details.

Brand	Alpinestars
Model	Bogota Pro Drystar
Type	Pants - Textile
Date purchased	20 January 2024
Tested by	AMCAF, Deakin University
Report approved by	MotoCAP Chief Scientist
Garment test reference	P24T14
Rating first published	May 2024
Rating updated	18 October 2024