



This MotoCAP safety rating applies to:


Brand DriRider Model Xena Jegging Type Pants - Textile Date purchased 19 June 2024 Sizes tested 10 and 12 Test garment gender Female All Purpose Style RRP \$269.00

Test Results Summary	Rating	Score
MotoCAP Protection Rating	*	20.4
Abrasion	1/10	0.42
Burst	5/10	551
Impact	6/10	42.6
MotoCAP Breathability Rating	***	0.523
Moisture Vapour Resistance	-	25.4
Thermal Resistance	-	0.221
Water resistance	N/A	N/A

This garment is fitted with impact protectors for the knees and hips. There are no vents to allow airflow movement through the garment.

Jacket and Pants - Crash Impact Risk Zones

This diagram is a pictorial representation of the crash impact risk Zones.

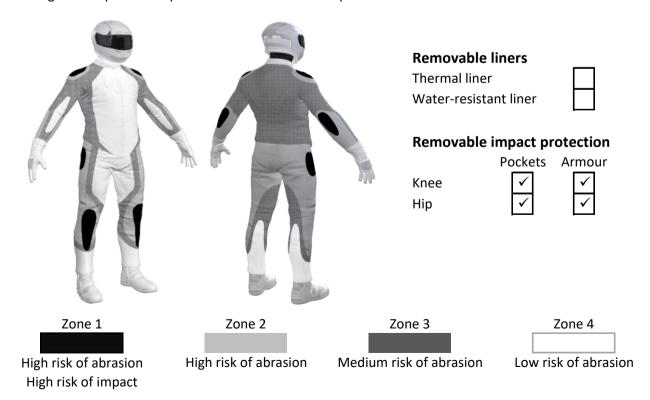



Abrasion Resistance

These pants were tested for abrasion resistance in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely abrasion performance of the materials in each zone calculated from the data in the table below. The colour coding is based on the worst performing material in each zone.



Abrasion Resistance Performance

Abrasion rating	1/10
Abrasion score	0.42

Determining Criteria	Area	Good	Acceptable	Marginal	Poor
High abrasion risk	Zones 1 & 2	> 5.6	3.0 - 5.6	1.3 - 2.9	< 1.3
Medium abrasion risk	Zone 3	> 2.5	1.8 - 2.5	0.8 - 1.7	< 0.8
Low abrasion risk	Zone 4	>1.5	1.0 - 1.5	0.4 - 0.9	< 0.4

Individual Abrasion Resistance Results: - The table below shows the test results for time to abrade through all layers of the materials. Calculated for each sample by Zone, type and area coverage of each material as a proportion of that Zone. Abrasion times are capped at a maximum of 10.00s.

Abrasion time for each test (seconds)

Abiasion time	ioi eacii test (sec	Jonasj						
Zones 1 & 2	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Material A	100%	0.34	0.28	0.72	0.34	0.43	0.41	0.42
Zone 3	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average
Material A	100%	0.34	0.28	0.72	0.34	0.43	0.41	0.42
Zone 4	Coverage (%)	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	L Average
Material A	100%	0.34	0.28	0.72	0.34	0.43	0.41	0.42

Details of materials used in pant

Material A Fabric shell and para-aramid fabric layer



Burst Strength

These pants were tested for burst strength in accordance with MotoCAP test protocols. The diagram below illustrates the burst strength results in terms of the likely performance of the garment in an impact and is a pictorial representation of the data from the table below.



Burst Strength Performance					
Burst rating	5/10				
Burst score	551				

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor
Burst strength	(kPa)	> 1000	800 - 1000	500 - 799	< 500

Individual Burst Strength Results: - The table below shows the burst pressure in kilopascals (kPA) for each sample tested by Zone and the average result for each zone.

Burst pressure for each seam (kPA)

Area	Sample 1	Sample 2	Sample 3	Sample 4	Sample 5	Sample 6	Average	
Zones 1 & 2	514	479	476	509	624	745	558	M
Zones 3 & 4	509	503	517	584	520	506	523	М



Impact Protection

These pants were tested for impact protection and coverage in accordance with MotoCAP test protocols. The diagram below is a visual indication of the likely performance of each impact protector calculated from the data in the table below. The colour coding is based on the worst performing score for average or maximum force for each impact zone. Areas shaded black are not considered for impact protection ratings.



Impact Protection Performance Impact rating 6/10 Impact score 42.6

Determining Criteria	Unit	Good	Acceptable	Marginal	Poor*
Impact force	(kN)	< 15	15 - 24	25 - 30	> 30

^{*} Poor may also indicate that no impact protector, or impact protector pocket is present in the garment

Impact Protector Results: - The table below shows the average and maximum force transmitted through each impact protector type in kilonewtons (kN) and their area of coverage as a proportion (%) of the Zone.

Impact protector type	Knee	Hip
Average force (kN)	22.2 A	18.2 A
Maximum force (kN)	28.1 M	28.2 M
Coverage of Zone 1 area	95%	150%
Coverage of Zone after displacement	80%	100%

Individual Impact Protector Results: - The table below shows the test results for each strike on individual impact protectors in kilonewtons (kN) and the position of the strike. Individual strike results are capped at a maximum of 50kN.

Force transfer for each impact strike (kN)

Impact protector type	Knee	,		Hip		
Strike location	Centre	Mid	Edge	Centre	Mid	Edge
Impact Protector 1	19.8	22.4	21.0	13.3	17.4	17.0
Impact Protector 2	20.0	22.5	28.1	15.3	18.4	23.3
Impact Protector 3	20.4	21.2	24.7	16.3	14.6	28.2



Breathability

These pants were tested for breathability following the MotoCAP test protocols. The table below shows the moisture vapour resistance and the thermal resistance values obtained.

Without removable li	With	water-resista	ant liner		
Breathability rating ★★★		Breat	hability rating	N/A	
Breathability score	0.523	Breathability score		N/A	
Moisture Vapour Resis	stance - R _{et} (kPa.m²/W)	1	2	Average	
Without removable liners	S	24.8	26.0	25.4	
With water-resistant line	r	N/A	N/A	N/A	
Thermal Resistance - F	R _{ct} (K.m²/W)	1	2	Average	
Without removable liners	S	0.217	0.225	0.221	
With water-resistant line	r	N/A	N/A	N/A	

Water spray and rain resistance

These pants have not been advertised as water-resistant so have not been tested for water spray and rain resistance.

Assessment Details.

Brand DriRider
Model Xena Jegging
Type Pants - Textile
Date purchased 19 June 2024

Tested by AMCAF, Deakin University Report approved by MotoCAP Chief Scientist

Garment test reference P25T01

Rating first published November 2024
Rating updated 8 November 2024